



HAL
open science

Influence of the nature and amount of carbonate additions on the thermal behaviour of geopolymers: A model for prediction of shrinkage

Svetlana Petlitckaia, Ameni Gharzouni, Eloise Hyvernaud, Nathalie Texier-Mandoki, Xavier Bourbon, Sylvie Rossignol

► To cite this version:

Svetlana Petlitckaia, Ameni Gharzouni, Eloise Hyvernaud, Nathalie Texier-Mandoki, Xavier Bourbon, et al.. Influence of the nature and amount of carbonate additions on the thermal behaviour of geopolymers: A model for prediction of shrinkage. *Construction and Building Materials*, 2021, 296, pp.123752. 10.1016/j.conbuildmat.2021.123752 . hal-03402174

HAL Id: hal-03402174

<https://unilim.hal.science/hal-03402174>

Submitted on 13 Jun 2023

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution - NonCommercial 4.0 International License

1 **Influence of the nature and amount of carbonate additions on the thermal behaviour of**
2 **geopolymers: A model for prediction of shrinkage**

3 Svetlana Petlitckaia¹, Ameni Gharzouni¹, Eloise Hyvernaud¹, Nathalie Texier-Mandoki²,
4 Xavier Bourbon², Sylvie Rossignol¹

5 ¹Institut de Recherche sur les Céramiques (IRCER), 12 rue Atlantis, 87068 Limoges Cedex,
6 France

7 ²Agence nationale pour la gestion des déchets radioactifs, 1-7 rue Jean-Monnet, 92298
8 Châtenay-Malabry Cedex, France

9 **Abstract:**

10 In order to develop fire resistant geopolymer materials, it is necessary to understand the
11 parameters controlling their thermal behavior such as the content of alkali or rare earth
12 cations. This study highlights the effect of carbonate nature and amount on the thermal
13 behavior of geopolymers in order to propose a model of thermal behaviour and predict
14 shrinkage. For this, various mixtures of kaolin and calcite and/or dolomite with different
15 percentages were calcined at 600 and 750°C. The feasibility of consolidated materials based
16 on these mixtures were evaluated and the thermal behavior of the obtained materials was
17 investigated. The characterization of the mixtures revealed the persistence of carbonates after
18 calcination at 600°C and their partial decomposition after calcination at 750°C. This fact was
19 explained in the case of high dolomite content by the existence of kaolinite gangue hindering
20 its decomposition. Consolidated materials were obtained from the different mixtures. After
21 thermal treatment at 1000°C, it was evidenced that the amorphous phase crystallizes to form
22 in a major part leucite. At lower available alkaline earth species (Ca²⁺ and Mg²⁺) content, only
23 wollastonite is formed and the shrinkage varies between 15 and 12%. However, at higher
24 content, different calcium and magnesium silicates can be formed such calico-olivine and
25 larnite in the case of calcite based materials and akermanite and merwinite for dolomite based

1 materials. This fact leads to lower shrinkage value (from 6 to 8%). Thus, it is possible to
2 control the thermal behavior and predict the shrinkage of geopolymer materials by controlling
3 the available alkaline earth cations.

4 **Keywords:** kaolin; calcite; geopolymer; dolomite; shrinkage

5 **1. Introduction**

6 Geopolymers are amorphous three-dimensional aluminosilicate material resulting from the
7 condensation of alumina and silica sources at high pH and low temperature (less than 100 °C)
8 [1]. They are characterized by high mechanical properties, stability at high temperatures [2],
9 wide range of applications [3] and low environmental impact [4]. Calcined clays are often
10 used as aluminosilicate source for geopolymer synthesis [5,6]. They are generally composed
11 of clays minerals, tectosilicates and carbonates. The understanding of the structural evolution
12 of each component of the clays and the interactions between them upon thermal treatment is
13 crucial to determine their reactivity and their effect on the geopolymer properties such as
14 thermal resistance. Carbonate is one of the most abundant and reactive compounds on earth.
15 Their thermal decomposition was intensively studied because of its great technological
16 importance [7]. Different parameters can influence the carbonate thermal decomposition such
17 as the nature and crystalline structure of carbonate and the experimental conditions such as
18 the sample weight, the particle size, the purge gas... [8]. Calcite is the most stable crystalline
19 form of calcium carbonate. It was proven to decompose at 750°C [9]. Dolomite was shown to
20 decompose in two stages. The first one yield to the formation of MgO and CaO. Then, the
21 CaO reacts to form calcite if sufficient CO₂ is available [10]. The interaction between
22 kaolinite and calcite upon thermal treatment was also studied [11, 12]. It was evidenced that
23 calcite endothermic peak on differential thermal analysis curve was impacted by the ratio of
24 kaolinite to calcite, the rate of CO₂ flow, the mixing, the heating rate and the volatiles evolved
25 during the dehydroxylation of kaolinite. Mitchell et al., [13] have proven that the heat

1 treatment of a mixture of 95% of kaolinite and 5% of calcite leads to the dehydroxylation of
2 kaolinite at 600°C, the decomposition of calcite to form lime (CaO) and portlandite (Ca(OH)₂)
3 if high humidity. From 900°C, it was evidenced the formation of anorthite (CaAl₂Si₂O₈) and
4 gehlenite (Ca₂Al(Al Si)O₇) and a beginning of formation of mullite (Al₆Si₂O₁₃) due to the
5 excess of metakaolinite. Mixtures of kaolin and dolomite were also studied with the same
6 proportions. Dolomite decomposed between 500 and 600 °C to form lime and periclase. At
7 900 °C, there is formation of gehlenite and anorthite, and persistence of periclase (MgO).
8 Other studies investigated kaolin and dolomite mixture to produce macroporous support for
9 ceramic membranes [14]. They have demonstrated that the sintering of kaolin was inhibited
10 by a percentage of dolomite higher than 10 wt. %. The crystalline phases formed by in situ
11 reaction sintering between 1150 and 1300 °C were mullite, cordierite (Al₃Mg₂AlSi₅O₁₈) and
12 anorthite.

13 Several studies [15,16,17,18] have focused on the effect of carbonates on geopolymer
14 synthesis and properties. Kutuk and Cetinkaya [19] have shown that kaolinite-calcite based
15 geopolymer materials can be successfully synthesized with various mass ratios of kaolinite
16 and using alkali silicate and NaOH. Yip et al., [20] have demonstrated that the addition of 20
17 wt.% of calcite and dolomite to metakaolin has a beneficial effect on the mechanical
18 properties of geopolymers. Above this percentage, the formation of geopolymer is limited and
19 the shrinkage is increased. Valentini et al., [21] also demonstrated that the moderate addition
20 of calcium carbonate (~ 25 wt. %) induces a significant increase of compressive strength.
21 However, the mechanical strength of geopolymer based on dolomite-metakaolin were found
22 to be lower than the calcite based one [22] due to lower dissolved calcium, particle size and
23 surface properties differences of dolomite compared to calcite. Although the effect of
24 carbonates on the mechanical properties was understood, their effect on the thermal behavior
25 is still complex and obvious as it depends on their amount and structure [23]. Dupuy et al.,

1 [24,25] have studied the thermal behavior of argillite based alkali-activated materials. The
2 studies evidenced that carbonates, essentially calcite and a low amount of dolomite, initially
3 present in the argillite, decompose during thermal treatment. Thus, available calcium reacts
4 with silica from the geopolymer amorphous phase to form wollastonite. Few studies
5 investigate the thermal evolution of geopolymers based on dolomite. Yan et al.,[26] evidenced
6 that the thermal treatment at 1000 °C of geopolymer foams based on metakaolin and dolomite
7 leads to the crystallization of leucite and the formation of periclase and lime resulting from
8 the decomposition of dolomite. Consequently, the presence of carbonates depending on their
9 nature and amount leads at high temperature of the formation of crystalline phases due to
10 solid state reaction. In previous work [27], it was demonstrated that geopolymers based on a
11 mixture of 33 wt. % of kaolin and 67 wt. % of argillite calcined at 750°C exhibit a high
12 thermal treatment resistance at 1000°C with an improvement of post-thermal treatment
13 strength. In order to understand this behavior and to propose a model of reactivity of this
14 sample, different mixtures based on kaolin and carbonates (calcite and/or dolomite) with
15 different proportions and calcination temperature (600 and 700°C) are investigated in the
16 present study. Thus, the novelty of the study is to give further insight on the thermal behavior
17 of geopolymer by understanding the role played by carbonate type and amount as well as the
18 calcination temperature of the aluminosilicate source and to propose a model of **thermal**
19 **behaviour**. In the discussion part, other formulations were added in order to validate the
20 obtained results.

21 **2. Experimental part**

22 **2.1. Raw materials and sample preparation**

23 The starting materials are reported in Table 1. The kaolin (Si/Al =1.44) contains traces
24 of calcite [28]. The mean diameter of kaolin is 20 µm and its water demand is about 530
25 µL/g. The BET specific surface area is 24 m²/g. The calcite (CaCO₃) and dolomite

1 (CaMg(CO₃)₂) have close water demand (310 and 273 μL/g respectively) with the different
2 particles size (2 and 14 μm respectively). CaCO₃ and CaMg(CO₃)₂ have both similar specific
3 surface areas (2 and 1 m²/g respectively). A commercial potassium silicate solution (Woellner
4 GmbH, Germany), with Si/K molar ratio of 1.7 and 79 % of water content, was used. The
5 activation solution, labelled S, was prepared by dissolving potassium hydroxide pellets in this
6 commercial solution in order to obtain a Si/K molar ratio of 0.58.

7 Five mixtures were prepared as shown in the CaO-MgO-2SiO₂Al₂O₃ ternary diagram
8 (**Figure 1**): (i) Two mixtures containing kaolin and calcite with weight percentages of calcite
9 equal to 10 and 50 wt. %, which corresponds to 21 and 70 molar percentages respectively (ii)
10 Two mixtures containing kaolin and dolomite with weight percentages of dolomite of 10 and
11 50 wt. % which corresponds to molar percentages of dolomite of 13 and 57 % and (iii) a
12 mixture containing kaolin (82 wt. %), calcite (13 wt. %) and dolomite (5 wt. %)
13 corresponding to molar percentages of 70, 25 and 5 %, respectively. The homogenization of
14 the mixtures was performed using a turbula mixer for 1 hour with a rotation speed of 72 rpm.
15 Then, the mixtures were calcined at 600 and 750 °C in a rotary oven (Carbolite Gero) for 1.5
16 hours except of the mixture containing calcite and dolomite which was only calcined at 750°C
17 in order to model the sample studied in previous work and showing optimal thermal resistance
18 at 1000°C [26]. The geopolymer samples are prepared by mixing the calcined mixtures with
19 the activation solution for 5 min. The K₂O/H₂O molar ratio is about 18.7. The samples are
20 cast in closed polystyrene mold (Ø =25 mm, H = 60 mm) and kept at room temperature for 7
21 days. Then, the thermal resistance of the different samples was evaluated at 1000°C with a
22 ramp of 5°/min, a dwell time of 15 min and a natural cooling in the furnace.

23 The adopted nomenclature to identify the raw mixtures and the geopolymer samples is M_x^T
24 and GM_x^T respectively, with M= ca and/or do, “ca” refers to calcite, “do” to dolomite and “x
25 to the weight percentage of each component. “T” indicates the calcination temperature (T=

1 600 or 750 °C). For example, $G_{Ca_{0.1}^{600}}$ geopolymer sample was obtained by mixing the
2 silicate solution with the mixture $ca_{0.1}^{600}$ composed of 90 wt.% of kaolin and 10 wt.% of
3 calcite calcined at 600 °C.

4 **2.2. Characterization techniques**

5 The particle size distributions of the raw materials and the mixtures were measured using a
6 laser particle size analyzer (Mastersizer-2000). The powders were dispersed in water.

7 Powder BET areas (m^2/g) were determined by N_2 adsorption at -195.85 °C using a
8 Micrometrics Tristar II 3020 volumetric adsorption/desorption apparatus. Prior to the
9 measurement, the samples were degassed at 200 °C under vacuum for 4h.

10 The water demand ($\mu L/g$) corresponds to the volume of water that can adsorbed by one
11 gram of powder before saturation. One gram of powder is deposited on a glass slide; water is
12 then added to the powder using a micropipette until visual saturation.

13 Differential thermal analysis (DTA) and thermogravimetric analysis (TGA) were
14 performed with a TA Instrument SDT Q600. Measurements were carried out under dry
15 airflow (100 mL/min) in a platinum crucible. About 30 mg of crushed samples were heated up
16 to 1000 °C with a rate of 10 °C/min and a dwelling time of 15 min. DTA-TGA coupled with
17 mass spectrometry was performed with a Netzsch STA 449F3 analyzer. For these
18 measurements, the samples were heated to 900 °C at a rate of 10 °C/min under an argon flow.

19 Fourier-Transform Infrared (FTIR) spectra were obtained with a ThermoFisher Scientific
20 Nicolet 380 spectrometer on the raw and calcined mixtures. Spectra were acquired in
21 transmission mode using KBr pressed discs (100 mg of KBr and 0.6 mg of sample). The
22 spectra were recording between 400 and 4000 cm^{-1} with a 4 cm^{-1} resolution and composed of
23 64 scans. The atmospheric CO_2 contribution was removed by using a straight line between
24 2400 and 2280 cm^{-1} . To allow comparison between the spectra, they were corrected using a
25 baseline and were normalized.

1 X-ray diffraction (XRD) experiments were performed with a Bruker-D8 Advance which
2 operates with Bragg-Brentano geometry and a $\text{CuK}\alpha_1\alpha_2$ detector. Data were recorded at a
3 range of 10° - 50° (2θ) with an angular step size of $0.02^\circ(2\theta)$ and a counting time of 0.26 s
4 per step. Joint Committee Powder Diffraction Standard (JCPDS) files were used for phase
5 identification.

6 Dilatometric measurements were performed under air with a vertical dilatometer Setsys
7 made by Setaram Instrumentation. The cylindrical samples ($d/H = 0.6$, where $d = 5$ mm and H
8 = 8 mm) were placed between two platinum/alumina holders during the analysis, and a
9 correction was applied to remove the contribution of the device/ holders. Samples were heated
10 until 900°C with a ramp of $5^\circ\text{C}/\text{min}$ in an air atmosphere and cooled with a ramp of 20
11 $^\circ\text{C}/\text{min}$

12 Environmental Scanning Electron Microscopy experiments were conducted using a FEI
13 QUANTA 450 FEG microscope at 15 kV. The geopolymers sample was directly placed in a
14 small MgO crucible covered with platinum paint (5 mm inner diameter). The thermocouple is
15 placed below the sample. The temperature was increased from 25 to 1000°C . The pressure is
16 maintained at 200 Pa. Many images of the sample surface were recorded during the
17 temperature variation.

18 **III. Results and discussion**

19 **1) Effect of carbonate nature and amount and the temperature of thermal** 20 **treatment on kaolin-carbonates mixtures**

21 In order to understand the thermal evolution of kaolin-carbonates mixtures, they were
22 characterized using thermal analysis, FTIR spectroscopy, XRD, chemical and physical
23 characterization. The effect of carbonate nature and amount and the temperature of thermal
24 treatment was highlighted.

25 ***a) Structural characterization***

1 FTIR measurements were also performed on the different mixtures. **Figure 4** shows the
2 FTIR spectra of the different mixtures. Whatever the non-calcined mixture (**Figure 4 A**),
3 bands related to OH stretching vibrations at 3396, 3650 and 3620 cm^{-1} and bending vibration
4 at 913 (Al_2OH) cm^{-1} [29] are observed. These bands are characteristic of kaolinite [30]. The
5 Si–O stretching vibrations are observed at 1100, 1034 and 1007 cm^{-1} [32]. The doublet at 797
6 and 778 cm^{-1} and the peak at 694 cm^{-1} are attributed to quartz [31]. For kaolin-calcite
7 mixtures, in addition to bands relative to kaolinite, asymmetric stretching vibrations (ν_3) at
8 1430 cm^{-1} and bending mode at 2511 ($2\nu_2 + \nu_4$), 1796 ($\nu_1 + \nu_4$), 875 (ν_2) and 712 (ν_4) cm^{-1} of
9 carbonate ions relative to calcite can be detected [32,33]. The intensity of these bands
10 increases with the increase of calcite content. For kaolin-dolomite mixtures, similar bands are
11 observed. Compared to calcite, dolomite displays characteristic bands at 2624 and 728 cm^{-1}
12 [34].

13 Whatever the mixture, after calcination at 600°C (**Figure 4 B**), the bands of kaolinite
14 disappear revealing the dehydroxylation of kaolin at this temperature. However, the band of
15 carbonates persists and broadens overlapping new contributions at 1397 cm^{-1} corresponding
16 to hydrogen carbonate HCO_3 [35] and another contribution at 1500 cm^{-1} attributed to the
17 asymmetric stretching vibrations of carbonate groups [36]. After calcination at 750°C (**Figure**
18 **4 C**), carbonates bands persist and in addition to that, peaks at 3700 and 3640 cm^{-1} appear due
19 to stretching vibrations O-H of $\text{Mg}(\text{OH})_2$ and $\text{Ca}(\text{OH})_2$ [37,38]. These findings are in
20 accordance with the results of thermal analysis discussed above. For kaolin-calcite mixtures,
21 the band is composed of three contributions at 1397, 1430 and 1500 cm^{-1} . For kaolin-dolomite
22 mixtures and especially with high dolomite content do_{0.5}⁷⁵⁰ sample, a strong and broad band is
23 observed in the region 1300-1600 cm^{-1} revealing structural transformations of dolomite.
24 Indeed, the band overlaps, in addition to the contributions at 1397 and 1500 cm^{-1} , a
25 contribution at 1450 cm^{-1} attributed to the non-decomposed dolomite and another contribution

1 at 1414 cm^{-1} which is related to CaCO_3 resulting from the decomposition of dolomite [7]. The
2 appearance of peaks at 2521 , 1800 , 874 and 713 cm^{-1} confirms the formation of CaCO_3 . To
3 emphasize all these contributions, the intensity of the band related to hydrogen carbonate
4 HCO_3^- at 1397 cm^{-1}
5 normalized by the intensity of the peak of water at 1640 cm^{-1} was plotted in function of the
6 number of moles of decomposed M^{2+} deduced from thermal analysis in **Figure 5A**. The
7 appearance of this band is due to the partial decomposition of carbonates and their possible
8 reaction with the air of atmosphere. In general, the intensity of hydrogen carbonate band
9 increases with the increase of the number of moles of non-decomposed carbonates except of
10 $\text{do}_{0.5}^{\text{T}}$ mixtures. In fact, at 600°C , for mixtures with low amount of carbonates, a low amount
11 of M^{2+} (1.81×10^{-5} and 1.53×10^{-5} mol for $\text{ca}_{0.1}^{600}$ and $\text{do}_{0.1}^{600}$ mixtures, respectively),
12 corresponds to low intensity of hydrogen carbonate band (2.56 and 1.29 for $\text{ca}_{0.1}^{600}$ and
13 $\text{do}_{0.5}^{600}$ mixtures, respectively). However, a higher content of calcite leads to the increase of
14 decomposed M^{2+} (7.74×10^{-5} mol for $\text{ca}_{0.5}^{600}$ mixture) and therefore the increase of the
15 normalized intensity of hydrogen carbonate bands (4.94). This is not the case of $\text{do}_{0.5}^{600}$
16 sample which shows a low intensity ratio (0.91). For mixtures calcined at 750°C , the same
17 evolution is noticed except of $\text{do}_{0.5}^{750}$ sample. The mixture containing calcite and dolomite
18 shows an intermediate position. These data suggest that a part of dolomite is surrounded of a
19 kaolinite gangue hindering its decomposition. Similarly, the intensity of the band at 1500 cm^{-1}
20 normalized by the intensity of the peak of water at 1640 cm^{-1} was plotted in function of the
21 number of moles of non-decomposed M^{2+} in **Figure 5B**. This band results also from a reaction
22 of carbonates with the air of atmosphere [39]. The same trend as observed in **Figure 5A** is
23 obtained showing the increase of the band intensity with the increase of the number of moles
24 of non-decomposed M^{2+} except of dolomite based mixtures $\text{do}_{0.5}^{\text{T}}$ samples). These mixtures

1 show low intensity of the band at 1500 cm^{-1} indicating lower formation of this carbonate
2 which means lower reaction with the atmosphere.
3 Consequently, the thermal treatment at 600 and 750 °C induces partial decomposition of
4 carbonates and the appearance of hydrogen carbonates. The decomposition of dolomite seems
5 to be hindered by a kaolinite gangue.

6 In order to obtain more accurate structural information about the mixtures based on calcite
7 and dolomite, XRD characterization was performed. The XRD patterns are presented in
8 **Figure 6**. For kaolin-calcite mixtures, after calcination at 600°C, kaolinite peaks disappear.
9 However, the peaks of calcite persist. The same observation is noted at 750°C with the
10 appearance of peaks related to CaO and Ca(OH)₂. These data complete the results of TGA
11 and FTIR analysis showing incomplete decomposition of calcite. For kaolin-dolomite
12 mixtures (do_x^T), the patterns evidence also the persistence of dolomite rays at 600°C and
13 750°C. However, at 750°C, the intensity of dolomite decreases drastically and rays relative to
14 calcite and MgO appear. These results also show the incomplete decomposition of dolomite at
15 750 °C and confirm the presence of a kaolinite gangue hindering the total decomposition of
16 dolomite.

17 2) Geopolymer materials

18 Feasibility tests of consolidated materials were carried out for all the studied mixtures. All
19 samples exhibit a consolidated appearance and a red-brown color due to the initial color of the
20 used kaolin containing Fe₂O₃ [40]. However, Gca_{0,5}⁷⁵⁰ mixture exhibits a high viscosity and a
21 flash consolidation which can be explained by high amount of reactive calcium [41]. A gel was
22 also observed on the surface of Gdo_{0,5}⁶⁰⁰ sample revealing a low amount of reactive
23 aluminium (low amount of kaolinite) and an excess of non-reacted silicate species from the
24 alkaline solution [27]. The XRD patterns of the samples shows an amorphous dome centered
25 at 28° characteristic of geopolymer materials as well as crystalline phases. For samples based

1 on calcined mixtures at 600°C, $G_{Ca_{0.25}^{600}}$ (**Figure 7A.a**) sample shows impurities of quartz,
2 anatase and hematite from kaolin [49] and persistence of calcite. $G_{Ca_{0.5}^{600}}$ sample (**Figure**
3 **7A.b**) exhibits the same phase but with higher intensity of calcite peaks. For kaolin-dolomite
4 mixtures based sample, dolomite and small peaks of calcite can be detected for $G_{D_{0.1}^{600}}$
5 (**Figure 7A.c**). Less intense peaks of dolomite and more intense peaks of calcite are found in
6 $G_{D_{0.5}^{600}}$ (**Figure 7A.d**) confirming the partial decomposition of dolomite. The XRD patterns
7 of samples based on calcined mixtures at 750°C highlight the persistence of calcite and the
8 formation of lime and portlandite in the kaolin-calcite based geopolymers (**Figure 7C.a,b**).
9 For kaolin-dolomite based geopolymers (**Figure 7C.c,d**), dolomite was also found in addition
10 to the formation of calcite, MgO and $Mg(OH)_2$. In the case of kaolin-dolomite-calcite based
11 geopolymer, (**Figure 7C.e**), dolomite, calcite, CaO, MgO, $Ca(OH)_2$ and $Mg(OH)_2$ are
12 detected.

13 Consequently, consolidated materials were successfully obtained from the different
14 mixtures of kaolin and carbonates calcined at 600 and 750°C. The mineral composition shows
15 the coexistence of an amorphous geopolymer network, residual non-decomposed carbonates
16 and reactive alkali earth cations resulting from decomposed carbonates.

17 **b. Thermal behavior**

18 In order to evaluate the thermal behavior of the synthesized geopolymers, they were heated
19 at 1000°C. Then, X-ray diffraction was performed to identify the mineralogical changes. The
20 chemical composition and the PDF files of the different mineral phases are reported in
21 **supplementary file**. Whatever the sample, crystalline phases can be detected. $G_{Ca_{0.1}^{600}}$
22 sample (**Figure 7B.a'**) shows the persistence of quartz and the formation of leucite
23 $K(AlSi_2O_6)$ and wollastonite ($CaSiO_3$). The formation of leucite ($KAlSi_2O_6$) was previously
24 evidenced in potassium based geopolymers [42,43]. Its formation is favored at higher
25 temperature (>800°C) and higher Si/Al molar ratio. Wollastonite was also found in the work

1 of Dupuy et al.[24] and results from a reaction at 780°C between silica from the amorphous
2 phase and available calcium from carbonate decomposition [44]. With the increase of calcite
3 content in $G_{Ca0.5}^{600}$ sample (**Figure 7B.b'**), the quartz peaks intensity decreases drastically
4 and more wollastonite is formed to the detriment of leucite and kalsilite due to higher
5 available calcium. Furthermore, others calcium silicates are formed such as Ca_2SiO_4 (α C2S)
6 calico-olivine (γ C2S), larnite (β C2S). Indeed, Larnite can be formed from a reaction between
7 quartz and lime from a temperature of 930 °C [45]. Calcio-olivine is the stable
8 Ca_2SiO_4 polymorph and is formed according to literature during cooling to room temperature
9 [48]. No differences can be detected for kaolin – dolomite based samples (**Figure 7D. c'and**
10 **d')**.

11 The same phases as at 600°C are detected for samples based on mixtures calcined at 750°C
12 (**Figure 7D. a',b' and c'**) except of $G_{D0.5}^{750}$ sample (**Figure 7D.d')** showing the formation
13 of additional phases such as akermanite ($Ca_2MgSi_2O_7$), merwinite ($Ca_3Mg(SiO_4)_2$) and
14 potassium magnesium silicate due to higher availability of magnesium and calcium. In the
15 case of kaolin-dolomite-calcite based geopolymer (**Figure 7D.e'**), quartz, leucite, kalsilite,
16 merwinite wollastonite and calico-olivine are detected.

17 In summary, the thermal treatment at 1000°C leads to the formation of crystalline phases
18 which depend on the initial chemical composition of the mixture. In fact, the amorphous
19 phase crystallizes to form potassium aluminium silicate, kalsilite and /or leucite. At lower
20 content of alkaline earth species (Ca^{2+} and Mg^{2+}), only wollastonite is formed. However, at
21 higher content different calcium and magnesium silicates can be formed.

22 Dilatometry measurements and DTA-TGA thermal analysis have been also carried on the
23 geopolymer samples. The shrinkage curves as well as the TGA curves of the samples are
24 presented in **Figure 8**. For kaolin –calcite based samples calcined at 600 °C, for $G_{Ca0.1}^{600}$ a
25 very small shrinkage (1%) is observed until 200°C and associated to an important weight loss

1 of 19.6 % and is due to the release of free and physisorbed water [46]. Then, a shrinkage of
2 1.5 % is detected until 800°C and can be attributed to the release of hydroxyl groups on the
3 surface [47]. The TGA curve shows a weight losses of 2.2 % between 600 and 800°C
4 attributed to the decomposition of the remaining calcite. A major shrinkage of 9.7 %, not
5 accompanied by a weight loss, is observed between 800 and 1000°C and attributed to two
6 phenomena i) the formation of a viscous flux and the ii) crystallization of crystalline phases
7 from 900°C which can be wollastonite and leucite according to XRD data [48]. A different
8 shrinkage curve is observed in the case of $G_{Ca_{0.5}}^{600}$ sample with an expansion between 600°C
9 to 800°C followed by a shrinkage of 5 % between 800 and 1000°C. The expansion is may be
10 due to the decomposition of carbonates. In fact the corresponding TGA curve shows three
11 weight losses of about 2.6, 2.9 and 8.6% in the temperature ranges 500-550, 550-650 and 650-
12 800°C, respectively. In order to identify the different weight losses, mass spectrometry
13 coupled with thermal analysis was performed. Only the obtained curve relative to the
14 mass/charge ratio (m/z) of 44 corresponding to the release of CO₂ is given in **supplementary**
15 **file**. As expected, three contributions of CO₂ between 500-550, 550-650 and 650-800°C are
16 shown. This results confirms the decomposition of three types of carbonates with different
17 crystallinities which can be attributed to hydrogen bicarbonate [49], mixed carbonates and
18 calcite. The hydrogen bicarbonate results from the interaction with humidity of the air and the
19 mixed carbonates from the exchange of alkali and alkali earth cations [52]. A slightly higher
20 total shrinkage (15 %) is observed in the case of $G_{D_{0.1}}^{600}$ sample. This is not the case of
21 $G_{D_{0.5}}^{600}$ sample showing the lowest shrinkage value (6.9 %). Three weight losses were also
22 observed in the TGA curves of 2.6, 4.0 and 6.5% in the temperature ranges 500-550, 550-650
23 and 650-800°C respectively. The formation of viscous flux begins at lower temperature
24 (712°C). This is due to the presence of a higher amount of alkali-earth cations (Ca²⁺ and
25 Mg²⁺) acting as flux lowering the viscous flux temperature [50]. At 750 °C, similar shrinkage

1 curves are observed except of $G_{Ca_{0.5}^{750}}$ showing an expansion from 600°C to 800°C then a
2 shrinkage of 4 % between 800 and 1000°C. The expansion could be explained by on one hand
3 the higher carbonate content which decomposes between 600 and 800°C and on the other
4 hand the elimination of residual stress caused by the flash consolidation of this sample such as
5 in glasses [51]. The TGA curve presents three weight losses (4.2, 3.7 and 6.4 in the
6 temperature ranges 500-550, 550-650 and 650-800°C respectively) corresponding to the
7 decomposition of hydrogen bicarbonate [52], mixed carbonates and calcite as previously
8 demonstrated. Once again, $G_{Do_{0.75}^{750}}$ shows a low shrinkage (8%) and the formation of
9 viscous flow and the crystallization of crystalline phases of lower temperature (700 and
10 800°C respectively). This results is in accordance with XRD data and literature showing
11 crystallisation of akermanite and merwinite at 850°C [53,54]. The TGA curve shows also
12 three weight losses of 2.6, 2.9 and 2.8% between 500-550, 550-650 and 650-800°C,
13 respectively.

14 The total shrinkage is plotted in function of the viscous flux temperature determined from
15 the first derivative of the shrinkage curve (maximum of viscous flux) (**Figure 9A**). In order to
16 validate the correlations, three extra formulations previously studied have been added, one
17 based on kaolin and argillite calcined at 750°C [26] and two formulation based on metakaolin
18 and Moroccan clays rich in carbonates [55]. The formulations were also added in the CaO-
19 MgO-2SiO₂Al₂O₃ ternary diagram (see supplementary file). A linear correlation is evidenced
20 showing the increase of the shrinkage value from 6 to 15.6% with the increase of viscous flux
21 temperature from 687 to 922 °C for $G_{Ca_{0.5}^{750}}$ and $G_{Do_{0.1}^{600}}$ samples respectively. The
22 shrinkage and the temperature of viscous flow are low for $G_{Ca_{0.5}^T}$ and $G_{Do_{0.5}^T}$ samples. This
23 fact can be explained in the first case by the formation of different calcium silicate
24 compounds as demonstrated by XRD lowering the shrinkage. In the second case, for high
25 dolomite content based samples $G_{Do_{0.5}^T}$, the presence of magnesium lowers the viscous flow

1 temperature. The silica is consumed for the formation of magnesium and calcium silicate and
2 will not be available to form a liquid phase which decreases the shrinkage [56]. Higher
3 shrinkage values and viscous flow temperature are obtained for low carbonates content based
4 samples ($Gca_{0.1}^T$ and $Gdo_{0.1}^T$). Indeed, silica from the amorphous phase remains free leading
5 to higher liquid phase and thus higher shrinkage. In order to verify this result, the shrinkage
6 values were also plotted in function of the molar ratio of the remaining M^{2+} in geopolymer
7 samples determined from TGA analysis (weight loss between 500-800°C) and the M^{2+}
8 initially present in the raw mixtures (**Figure 9B**). It is shown a decrease of the shrinkage in
9 function of this ratio. For low carbonates content samples, whatever the calcination
10 temperature, the molar ratios varies between 0.06 and 0.13 with shrinkage values between 15
11 and 12% which corresponds to $Gdo_{0.1}^{600}$ and $Gca_{0.1}^{750}$ samples. For high carbonates content
12 samples, the molar ratios varies between 0.18 and 0.44 between which corresponds to a low
13 shrinkage value varying between 6 and 8 % for $Gca_{0.5}^{750}$ and $Gdo_{0.5}^{750}$ samples, respectively.
14 Indeed, the increase of available alkaline earth cations leads to the creation of non-bridging
15 oxygens NBO and disorder favoring the formation of crystalline phases [57]. In fact, they will
16 react at high temperature to form calcium and/or magnesium silicates which reduces the
17 shrinkage. SEM photos at the temperature of viscous flux temperature appearance (**Figure**
18 **9A**) and at 1000°C are reported in **Figure 10**. Three examples of sample were selected. For
19 low carbonates content such as $Gdo_{0.1}^{750}$ sample (**Figure 10a**) exhibiting high viscous flux
20 temperature and high shrinkage (878°C and 12 % respectively), the observed microstructure
21 is similar to typical metakaolin based geopolymer showing glass-like structure with high
22 porosity content [58]. For $Gca_{0.13}do_{0.05}^{750}$ sample (**Figure 10b**), having intermediate values of
23 viscous flux temperature and shrinkage (813°C and 10% respectively) it is observed the
24 sintering of the amorphous phase and also the appearance of crystals and fibrous particles. For
25 high carbonate content such as $Gca_{0.5}^{750}$ sample (**Figure 10c**) characterized by low viscous

1 flux temperature and shrinkage value (687°C and 6 % respectively). More heterogeneous
2 microstructure is observed indicating the formation of different crystalline phases. These
3 observations corroborate the data in Figure 9. Consequently, it is possible to control the
4 thermal shrinkage by the control of the carbonates content (nM^{2+}) in the geopolymer and the
5 well knowledge of the raw materials.

6

7 **Conclusion**

8 This study aims to propose a model of thermal behaviour of geopolymer materials by
9 investigating the effect of carbonate nature and amount and the calcination temperature of the
10 aluminosilicate source. For this, two mixtures of kaolin and calcite (10 and 50 wt.% of
11 calcite), two mixtures of kaolin and dolomite (10 and 50 wt.% of dolomite) calcined at 600
12 and 750°C and a mixture composed of kaolin, dolomite (5 wt.%) and calcite (13 wt.%)
13 calcined at 750°C were studied. The characterization of these mixtures by thermal analysis,
14 FTIR spectroscopy and XRD evidenced the complete dehydroxylation of kaolin and the
15 persistence of carbonates after calcination at 600°C. Partial decomposition of calcite and
16 dolomite was proven after calcination at 750°C. Furthermore, it was demonstrated that a
17 kaolinite gangue can hinder the decomposition of dolomite in the case of mixture composed
18 of 50 wt. % of dolomite. Then, the thermal behavior at 1000°C of the obtained consolidated
19 materials based on these mixtures was evaluated. Two different behaviours can be
20 distinguished:

21 i) Geopolymers based on low carbonates content exhibit high shrinkage (from 12 to 16%)
22 and viscous flow at high temperature. They are characterized by the formation of potassium
23 aluminium silicate, kalsilite, leucite and wollastonite.

1 ii) Geopolymers based on high carbonates content exhibit lower shrinkage (from 6 to 8%),
2 the appearance of viscous flow at lower temperature and the crystallisation of different
3 additional phases (calcium and/or magnesium silicates).

4
5

6 **Acknowledgment**

7 Project supported by Andra under the "Investing in the Future Programme" ("Investissement
8 d'Avenir") - Selected under the Andra Call for Projects: "Optimisation of post-dismantling
9 radioactive waste management", organised in cooperation with the French National Research
10 Agency (ANR).

11

12 **References**

-
- [1] J. Davidovits, Geopolymers, inorganic polymeric new materials, *J. Therm. Anal.* 37 (1991) 1633-1656.
- [2] K.J.D. MacKenzie, , What are these things called geopolymers? A physico-chemical perspective. *Adv. Ceram. Matrix Composites IX*, *Ceram. Trans.* 153 (2003) 175–186.
- [3] K.J. D. MacKenzie, Inorganic polymers (geopolymers), In *Encyclopedia of Polymer Science and Technology*, Wiley (2017) 1-31. DOI:10.1002/0471440264.pst165.pub2. ISBN 9780471440260.
- [4] Y.M Liew, H. Kamarudin, A.M. Mustafa Al Bakri, M. Luqman, I . Khairul Nizar, C.Y. Heah. Investigating the possibility of utilization of kaolin and the potential of metakaolin to produce green cement for construction purposes. *Aust J Basic Appl Sci.* 5 (2011) 441–9.
- [5] A. Buchwald, M. Hohman, K. Posern, and E. Brendler. The suitability of thermally activated illite/smectite clay as raw material for geopolymer binders. *Appl. Clay. Sci.* 46 (2009) 300–304.
- [6] X.Yao, Z. Zhang, H. Zhu, and Y.Chen. Geopolymerization Process of Alkali-Metakaolinite Characterized by Isothermal Calrimetry. *Thermochim. Acta.* 493 (2009) 49–54.

-
- [7] A. K. Galwey, M. E. Brown, Chapter 12 Decomposition of carbonates, [Studies in Physical and Theoretical Chemistry](#) 86 (1999) 345-364.
- [8] A. R. Salvador, E.G. Calvo, C.B. Aparicio, Effects of sample weight, particle size, purge gas and crystalline structure on the observed kinetic parameters of calcium carbonate decomposition, *Thermochim. Acta.* 143 (1989) 339-345.
- [9] K.S.P. Karunadasa, C.H. Manoratne, H.M.T.G.A. Pitawala, R.M.G. Rajapakse, Thermal decomposition of calcium carbonate (calcite polymorph) as examined by in-situ high-temperature X-ray powder diffraction, *J. Phys. Chem. Solids.* 134 (2019) 21-28.
- [10] A.I. Rat'ko, A.I. Ivanets, A. I. Kulak, E.A. Morozov, I.O. Sakhar, Thermal decomposition of natural dolomite, *Inorg. Mater.* 47 (2011) 1372-1377.
- [11] R.C. Mackenzie, A.A. Rahman, Interaction of kaolinite with calcite on heating: I. instrumental and procedural factors for one kaolinite in air and nitrogen, *Thermochim. Acta.* 121 (1987) 51-69,
- [12] R.C. Mackenzie, A.A. Rahman, H.M. Moir, Interaction of kaolinite with calcite on heating. II. mixtures with one kaolinite in carbon dioxide, *Thermochimic. Acta.* 124 (1988) 119-127.
- [13] R. S. Mitchell, S.C. Hart, Heated Mineral Mixtures Related to Ancient Ceramic Pastes X-ray Diffraction Study, *Archaeological Chemistry IV*, 1989, pp 145-155
- [14] J. Zhou, X. Zhang, Y. Wang, A. Larbot, X. Hu, Elaboration and characterization of tubular macroporous ceramic support for membranes from kaolin and dolomite, *J. Porous Mater.* 17 (2010) 1-9.
- [15] A.S. Sauffi, W.M.W. Ibrahim, R. Ahmad, N.A.M. Mortar, F.A. Zaidi & W.W.A. Zailani, A review of morphology analysis on dolomite as an additive material in geopolymer, *IOP Conf. Series : Mater.Sci. Eng.* 743 (2020) 012024.
- [16] E.A. Aizat, A.M.M. Al Bakri, Y.M. Liew, C.Y. Heah, Chemical composition and strength of dolomite geopolymer composites, *AIP Conference Proceedings*, 1885 (2017) 020192.
- [17] A.S. Ouda, M. Gharieb, Development the properties of brick geopolymer pastes using concrete waste incorporation dolomite aggregate, *J. Build. Eng.* 27 (2020) 1-12.
- [18] A. Aboulayt, M. Riahi, M. Ouzzani Touhami, H. Hannache, M. Gomina, R. Moussa, Properties of metakaolin based geopolymer incorporating calcium carbonate, *Adv. Powder Technol.* 28 (2017) 2393 -2401.

-
- [19] N. Kutuk, S. Cetinkaya, Effect of kaolinite mass ratio on compressive strength of kaolinite-calcite based geopolymer, *International Journal of Computation and Experimental Science and Engineering*. 3 (2017) 25-28.
- [20] C.K. Yip, J.L. Provis, G.C. Lukey, J.S.J. van Deventer, Carbonate mineral addition to metakaolin-based geopolymers, *Cem. Concr. Compos.* 30 (2008) 979-985,
- [21] L. Valentini, S. Contessi, M.C. Dalconi, F. Zorzi, E. Garbin, Alkali-activated calcined smectite clay blended with waste calcium carbonate as a low-carbon binder, *J. Clean. Prod.* 184 (2018) 41-49.
- [22] E.A. Azimi, M.M.A.B. Abdullah, L.Y. Ming, H.C. Yong, K. Hussin, I.H. Aziz, Review of dolomite as precursor of geopolymer materials. *MATEC Web of Conferences*, 78 (2016) 01090.
- [23] A. Natali Murri, W.D.A. Rickard, M.C. Bignozzi, A. van Riessen, High temperature behaviour of ambient cured alkali-activated materials based on ladle slag, *Cement. Concrete. Res.* 43 (2013) 51-61.
- [24] C. Dupuy, A. Gharzouni, N. Texier-Mandoki, X. Bourbon, S. Rossignol, Alkali-Activated Materials Based on Callovo-Oxfordian Argillite: Formation, Structure and Mechanical Properties, *J. Ceram. Sci. Technol.* 9 (2018) 127-140, DOI: 10.4416/JCST2017-0008
- [25] C. Dupuy, A. Gharzouni, I. Sobrados, N. Texier-Mandoki, X. Bourbon, S. Rossignol, Thermal resistance of argillite based alkali-activated materials. Part 2: Identification of the formed crystalline phases, *Mater. Chem. Phys.* 218 (2018) 262-271.
- [26] S. Yan, F. Zhang, S. Wang, P. He, D. Jia, J. Yang, Crystallization behavior and mechanical properties of high open porosity dolomite hollow microspheres filled hybrid geopolymer foams, *Cem. Concr. Compos.* 104, (2019) 103376.
- [27] M. Tognonvi, S. Petlitckaia, A. Gharzouni, M. Fricheteau, N. Texier-Mandoki, X. Bourbon, S. Rossignol, High-temperature, resistant, argillite based, alkali activated materials with improved post-thermal treatment mechanical strength. *Clays Clay Miner.* 68 (2020) 211–219.
- [28] A. Gharzouni, (2016). Contrôle de l'attaque des sources aluminosilicates par la compréhension des solutions alcalines. PhD. thesis, University of Limoges, Limoges, France, pp 227.
- [29] P. Djomgoue, D. Njopwouo, FT-IR Spectroscopy Applied for Surface Clays Characterization, *J. Surf. Eng. Mater. Adv. Technol.* 3 (2013) 275-282.

-
- [30] J. Madejova, FTIR techniques in clay mineral studies. *Vib.Spectrosc.* 31(2003) 1 –10.
- [31] S. K. Petrovskii, O. G. Stepanova, S. S. Vorobyeva, T. V. Pogodaeva, A. P. Fedotov, The use of FTIR methods for rapid determination of contents of mineral and biogenic components in lake bottom sediments, based on studying of East Siberian lakes, *Environ. Earth. Sci.* 75 (2016) 226.
- [32] S. Gunasekaran, G. Anbalagan, Spectroscopic characterization of natural calcite minerals, *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy.* 68(2007) 656-664.
- [33] HuaNc, C., Konn, P. Infrared study of the carbonate minerals. *Am. Miner.* 45 (1960) 371-324.
- [34] J. Ji, Y. Ge, William Balsam, J. E. Damuth, Jun Chen, Rapid identification of dolomite using a Fourier Transform Infrared Spectrophotometer (FTIR): A fast method for identifying Heinrich events in IODP Site U1308, *Marine Geology*, 258 (2009) 60-68.
- [35] E.M Köck, M. Kogler, T. Bielz, B. Klötzer, S. Penner In Situ FT-IR Spectroscopic Study of CO₂ and CO Adsorption on Y₂O₃, ZrO₂, and Ytria-Stabilized ZrO₂, *J. Phys. Chem. C* 2013, 117, 34 (2013) 17666-17673.
- [36] A. Grzechnik, H. D. Zimmermann, R. L. Hervig, P. L. King, P.F. McMillan, FTIR micro-reflectance measurements of the CO₃²⁻ ion content in basanite and leucitite glasses, *Contrib. Mineral. Petrol.* 125 (1996) 311–318.
- [37] M. Khachani, A. El Hamidi, M. Halim, S. Arsalane Non-isothermal kinetic and thermodynamic studies of the dehydroxylation process of synthetic calcium hydroxide Ca(OH)₂, *J. Mater. Environ. Sci.* 5 (2) (2014) 615-624
- [38] A. Pilarska, M. Wysokowski, E. Markiewicz, Teofil Jesionowski, Synthesis of magnesium hydroxide and its calcinates by a precipitation method with the use of magnesium sulfate and poly(ethylene glycols), *Powder Technol.* 235 (2013) 148-157
- [39] A. K. Pathak, T. Mukherjee and D. K. Maity, IR Spectra of Carbonate-Water Clusters, CO₃⁻² (H₂O)_n: A Theoretical Study, Synthesis and Reactivity in Inorganic, Metal-Organic, and Nano-Metal Chemistry, 38(2008)76–83
- [40] A. Gharzouni, I. Sobrados, E. Joussein, S. Baklouti, S. Rossginol, Control of polycondensation reaction generated from different metakaolin and alkaline solution, *J. Ceram. Sci. Technol.*, 8 (2017) 365-376, 10.4416/JCST2017-00040
- [41] C. Dupuy, A. Gharzouni, N. Mandoki, X. Bourbon, S. Rossginol, Alkali-Activated Materials based on Callovo-Oxfordian Argillite: Formation, Structure and Mechanical Properties, *J. Ceram. Sci. Technol.*, 9(2) (2018) 127-140

-
- [42] V. F.F. Barbosa, K.J.D. MacKenzie, Synthesis and thermal behaviour of potassium sialate geopolymers, *Mater. Lett.* 57 (2003) 1477-1482.
- [43] P. Duxson, G.C. Lukey, J.S.J. van Deventer, The thermal evolution of metakaolin geopolymers: Part 2 – Phase stability and structural development. *J. Non-Cryst. Solids.* 353 (2007) 2186-2200.
- [44] Q. Yu, K. Sawayama, S. Sugita, M. Shoya, Y. Isojima The reaction between rice husk ash and Ca(OH)₂ solution and the nature of its product, *Cement Concr. Res.*, 29 (1999), pp. 37-43
- [45] N. Bohme, K. Hauke, M. Neuroth, T. Geisler, In situ Raman imaging of high-temperature solid-state reactions in the CaSO₄–SiO₂ system, *Int. J. Coal. Sci. Technol.* 6(2) (2019) 247–259.
- [46] W. Rickard, A. van Riessen, J. Temuujin, Thermal analysis of geopolymer pastes synthesised from five fly ashes of variable composition, *J. Non-Cryst. Solids.* 358 (2012) 1830-1839.
- [47] P. Duxson, G.C. Lukey, J.S.J. van Deventer, Physical evolution of Na-geopolymer derived from metakaolin up to 1000 °C. *J Mater Sci.* 42 (2007) 3044–3054
- [48] J.L. Bell, P.E. Driemeyer and W.M. Kriven, Formation of Ceramics from Metakaolin-Based Geopolymers. Part II: K-Based Geopolymer. *J. Am. Ceram. Soc.* 92 (2009) 607-615.
- [49] I. C. Hisatsune and T. Adi, Thermal Decomposition of Potassium Bicarbonate, *J. Phys. Chem.* 74 (1970) 2875–2877.
- [50] C. Dupuy, Valorisation de l'argilite du Callovo-Oxfordien sous forme de liant alcalinement activé dans le but de développer un coulis injectable PhD. thesis, University of Limoges, Limoges, France, 2019.
- [51] J. Zarzycki, Glasses and the vitreous state, Cambridge University Press, 1991.
- [52] I. C. Hisatsune and T. Adi, Thermal Decomposition of Potassium Bicarbonate, *J. Phys. Chem.* 74 (1970) 2875–2877.
- [53] Y. J. Zhang, S. Li, Y. Chao Wang, D. L. Xu, Microstructural and strength evolutions of geopolymer composite reinforced by resin exposed to elevated temperature, *J. Non-Cryst. Solids,* 358, (2012) 620-624.
- [54] M. Mohabbi Yadollahi & Murat Dener, Investigation of elevated temperature on compressive strength and microstructure of alkali activated slag based cements, *European Journal of Environmental and Civil Engineering,* (2019) DOI: 10.1080/19648189.2018.1557562

-
- [55] A.El Khomsi, A. Gharzouni, N. Kandri, A. Zerouale, S. Rossignol, Properties of Geopolymer Composites from two Different Moroccan Clays. *Ceramics in Modern Technologies*. 2 (2020)10.29272/cmt.2020.0001.
- [56] Claudia Lira, Marcio C. Fredel, Mauro D. M. da Silveira, Orestes E. Alarcon, Effect of carbonates on firing shrinkage and on moisture expansion of porous ceramics tiles. (1998)10.13140/2.1.2102.3522.
- [57] Reddy, A.A., Tulyaganov, D.U., Kharton, V.V. et al. Development of bilayer glass-ceramic SOFC sealants via optimizing the chemical composition of glasses—a review. *J Solid State Electrochem*. 19 (2015) 2899–2916. <https://doi.org/10.1007/s10008-015-2925-5>
- [58] P. Payakaniti, N. Chuewangkam, R. Yensano, S. Pinitsoontorn, P.Chindaprasirt, Changes in compressive strength, microstructure and magnetic properties of a high-calcium fly ash geopolymer subjected to high temperatures, *Constr. Build. Mater*. 265 (2020) 120650.

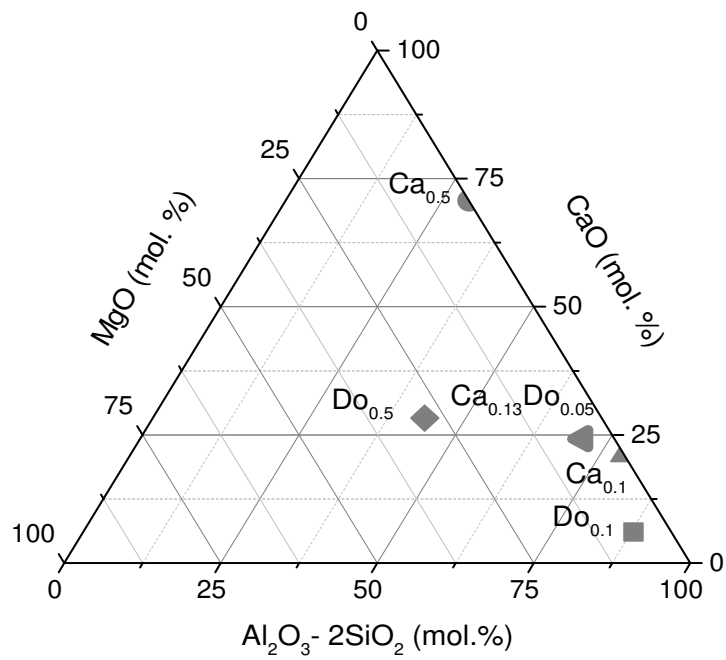


Figure 1 : Chemical composition of the mixtures ca_xdo_y in the CaO – MgO – Al₂O₃-2SiO₂ ternary diagram $ca_{0.1}$ (▲), $ca_{0.5}$ (●), $do_{0.1}$ (■), $do_{0.5}$ (◆) and $ca_{0.13}do_{0.05}$ (◄)




A**B****C**

Figure 2 : TGA curves of $Ca_xDo_y^T$ mixtures (A) before and after calcination at (B) 600 and (C) 750 °C for $Ca_{0.1}$ (---), $Ca_{0.5}$ (...), $Do_{0.1}$ (-.-.-), $Do_{0.5}$ (-.-.-.-), $Ca_{0.13}Do_{0.05}$ (—)





Figure 3 : Value of decomposition temperature of carbonates of $ca_xdo_y^T$ mixtures calcined at 600 (empty) and 750 °C (black) ($ca_{0.1}$ (○, ●), $ca_{0.5}$ (△, ▲), $do_{0.1}$ (□, ■), $do_{0.5}$ (◇, ◆); $ca_{0.13}do_{0.05}$ (◀))

A

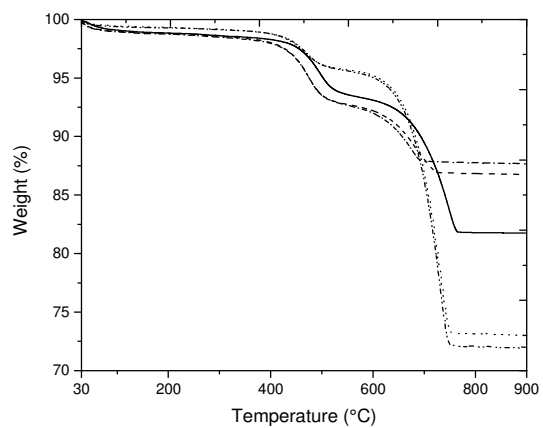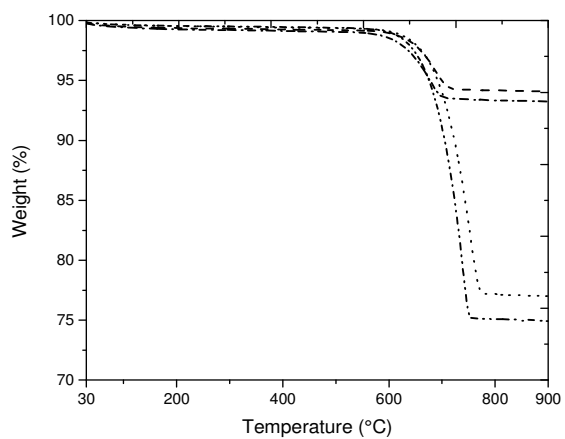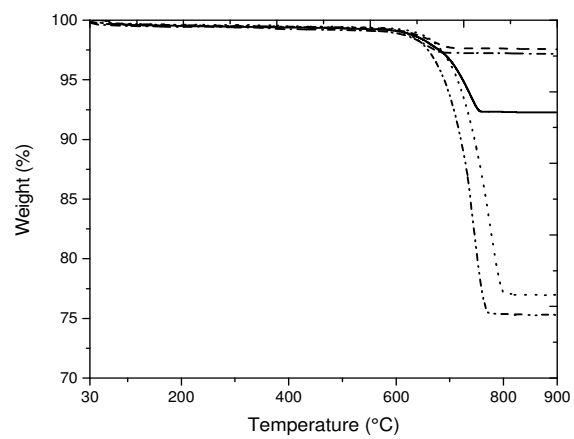

B

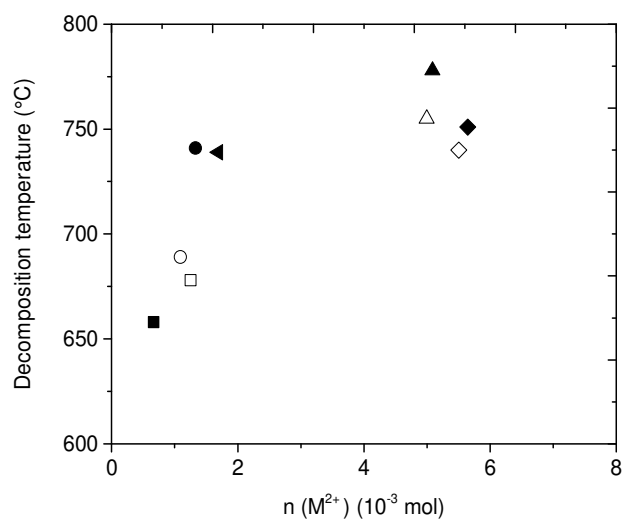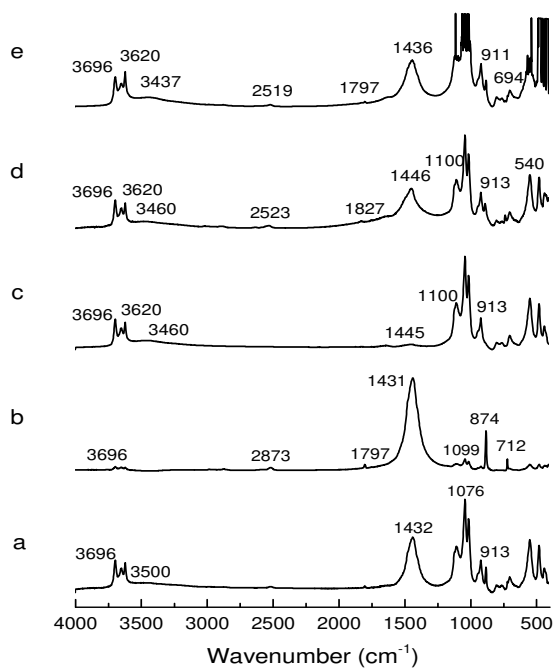C

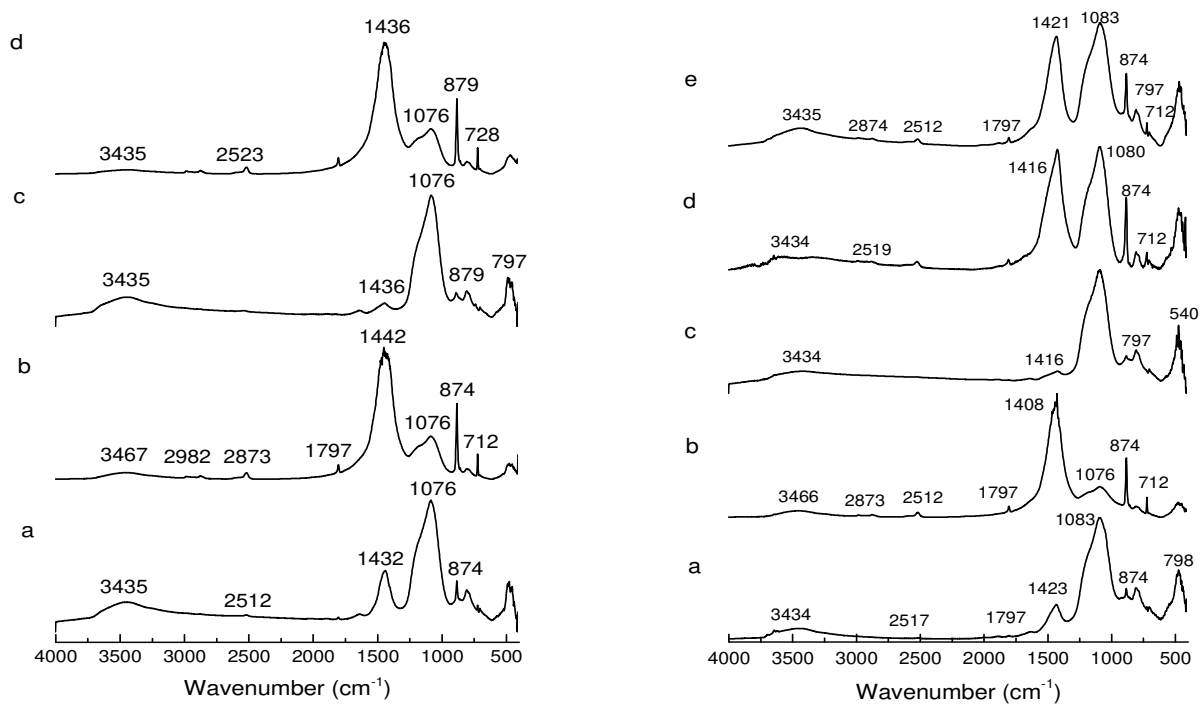
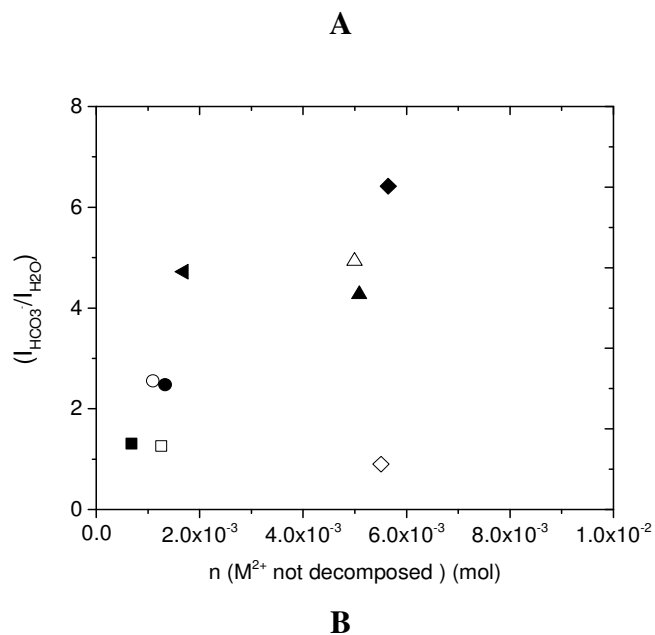


Figure 4: FTIR spectra of mixtures $Ca_xDo_y^T$ (A) non-calcined, calcined at (B) 600 and (C) 750°C (with (a) $Ca_{0.1}$, (b) $Ca_{0.5}$, (c) $Do_{0.1}$, (d) $Do_{0.5}$ and (e) $Ca_{0.13}Do_{0.05}$)



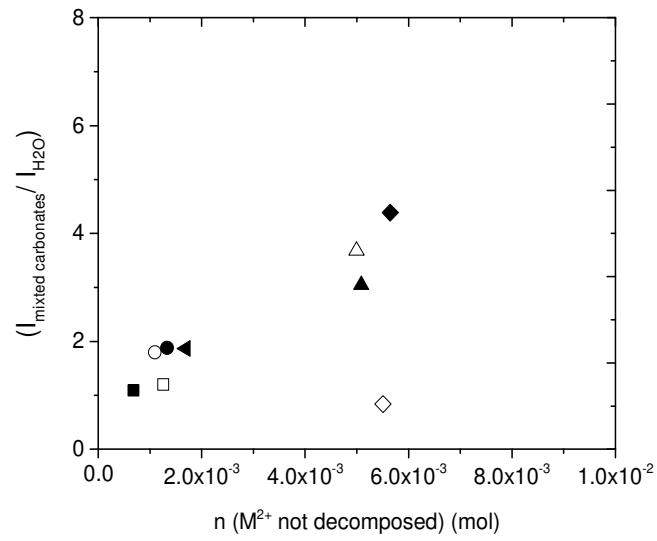


Figure 5 : Ratio of $\frac{I_{HCO_3} (1397 \text{ cm}^{-1})}{I_{H_2O} (1620 \text{ cm}^{-1})}$ (A) and $\frac{I_{mixed \ carbonates} (1500 \text{ cm}^{-1})}{I_{H_2O} (1620 \text{ cm}^{-1})}$ (B) for the mixtures $ca_xdo_y^T$ calcined at 600 °C (empty) and 750 °C (black) ($ca_{0.1}$ (○,●), $ca_{0.5}$ (△,▲), $do_{0.1}$ (□,■), $do_{0.5}$ (◇,◆) and $ca_{0.13}do_{0.05}$ (◄).

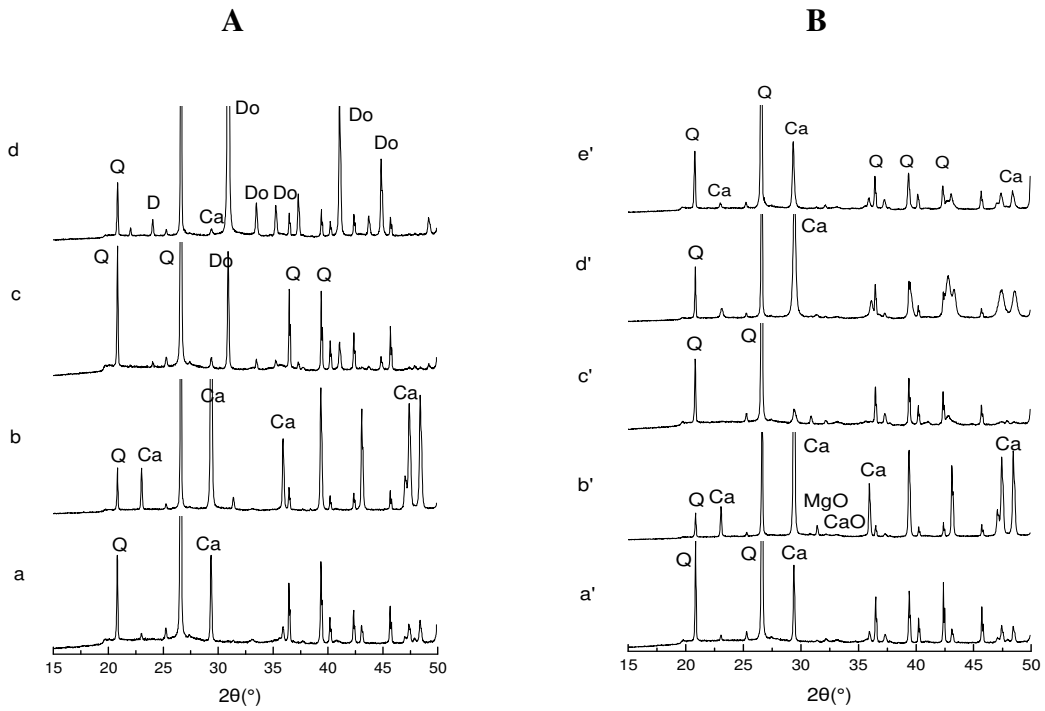


Figure 6 : XRD patterns of mixtures $ca_x do_y^T$ where $ca_{0.1}$ (a, a'), $ca_{0.5}$ (b, b'), $do_{0.1}$ (c, c'), $do_{0.5}$ (d, d') and $ca_{0.13} do_{0.05}$ (e, e') calcined at (A) 600 and (B) 750 °C (*Q*-quartz, *Ca*-calcite, *Do*-dolomite)

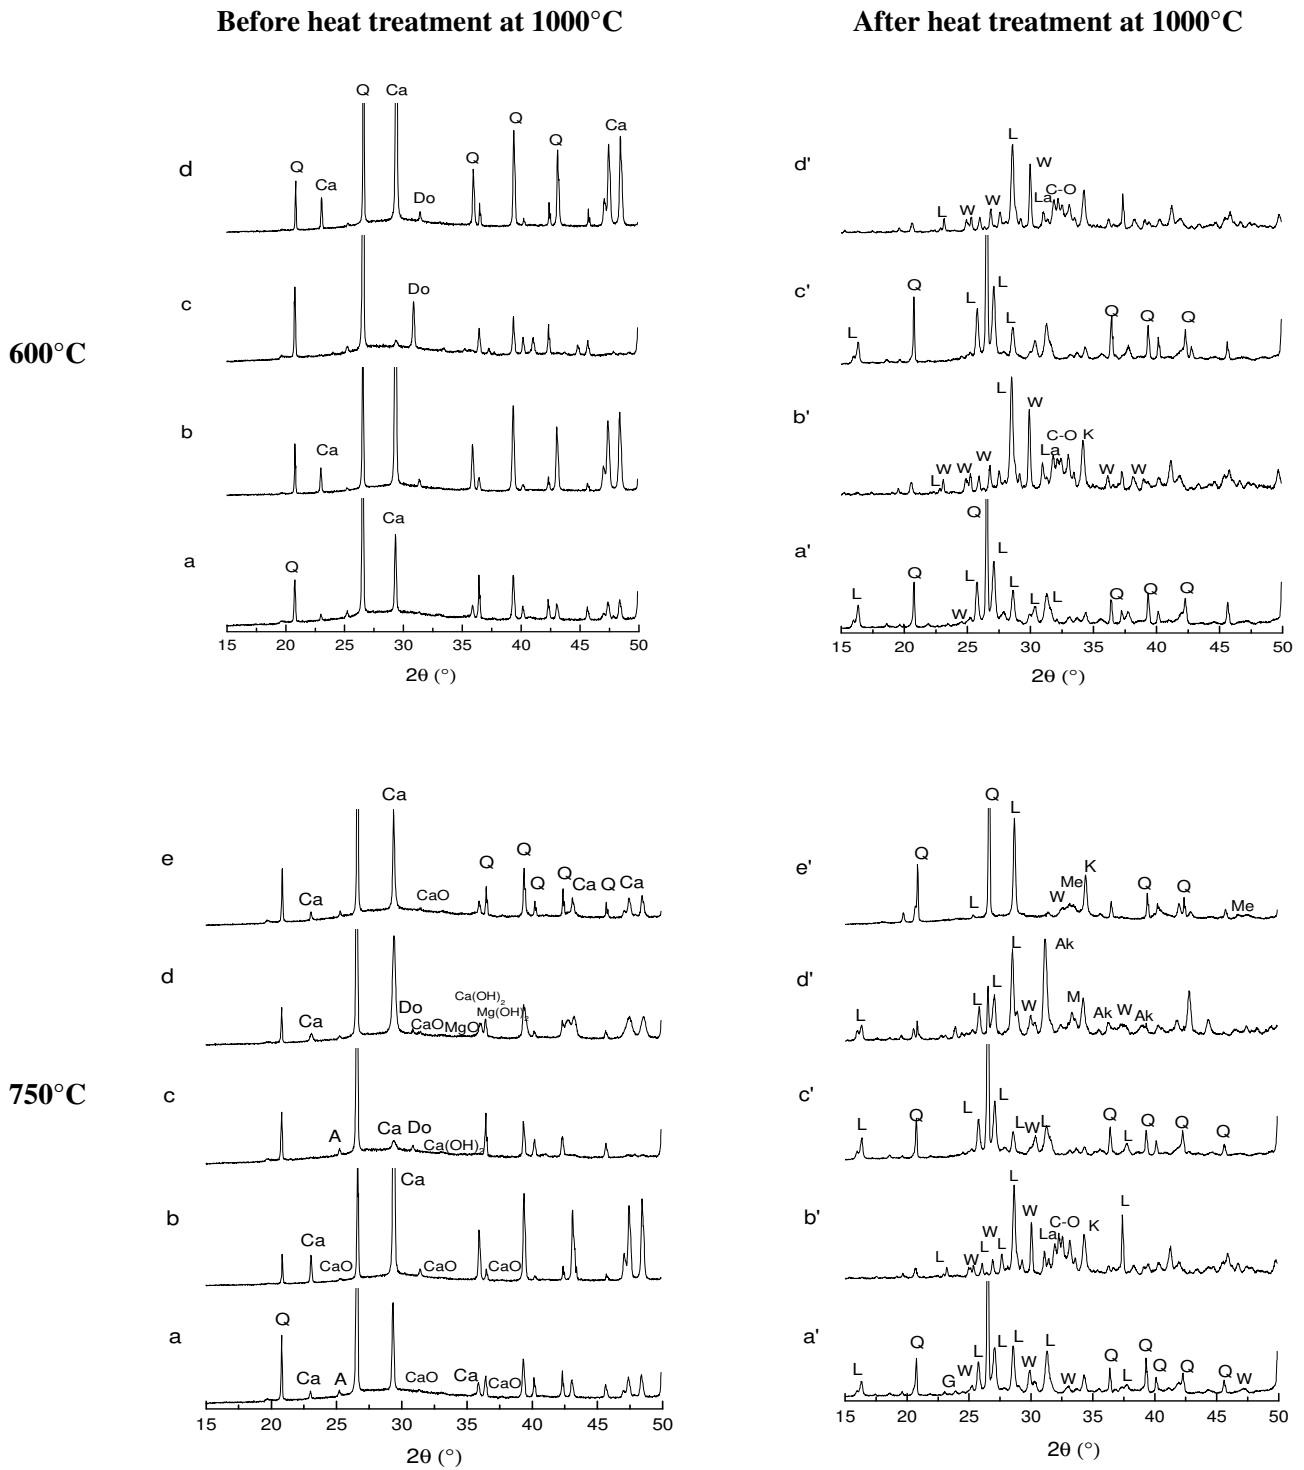


Figure 7: XRD patterns of geopolymers $Gca_xdo_y^T$ based on the mixtures (a, a') $ca_{0.1}, ca_{0.5}$, (b, b') $do_{0.1}$, (c, c'), (d, d') $do_{0.5}$ and (e, e') $ca_{0.13}do_{0.05}$ calcined at $600^\circ C$ and $750^\circ C$ before and after heat treatment at $1000^\circ C$ (Q-quartz, Ca-calcite, Do-dolomite, A-anatase, L-leucite, G-gehlenite, W-wollastonite, C-O – calcio-olivine, La-larnite, K-kalsilite, Me – merwinite, Ak - akermatite)

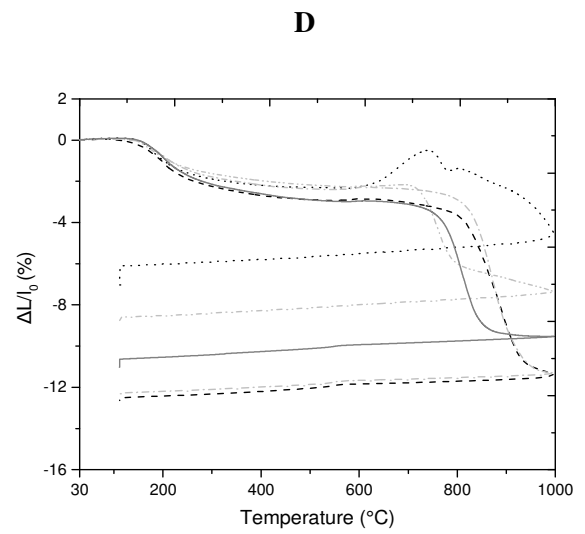
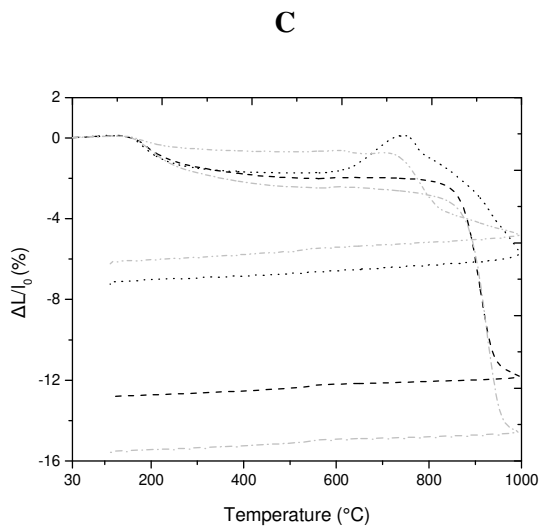
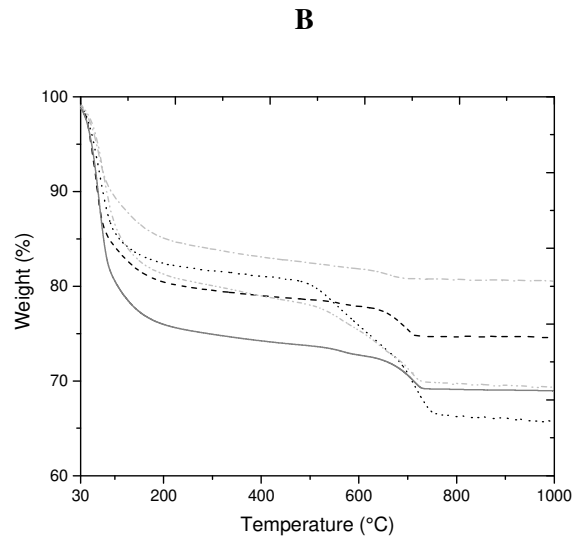
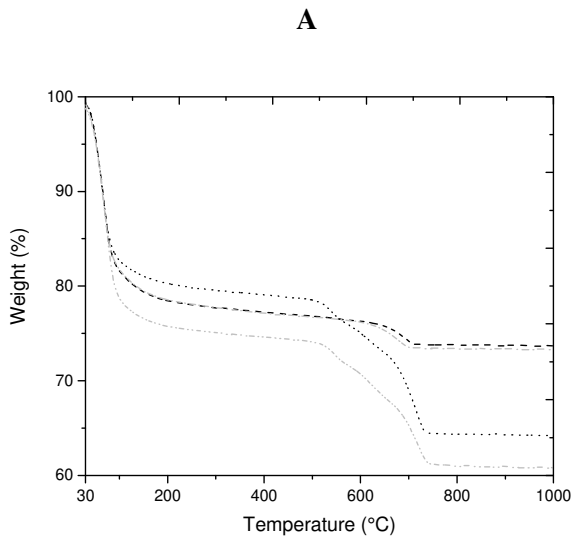


Figure 8: (A, B) TGA and (C, D) dilatometric curves of geopolymers samples based on the mixture $\text{Ca}_x\text{Do}_y\text{T}$ calcined at (A, C) 600 and (B, D) 750°C with $\text{ca}_{0.1}$ (---), $\text{ca}_{0.5}$ (...), $\text{do}_{0.1}$ (-.-.-), $\text{do}_{0.5}$ (-.-.-.-) and $\text{ca}_{0.13}\text{do}_{0.05}$ (—).

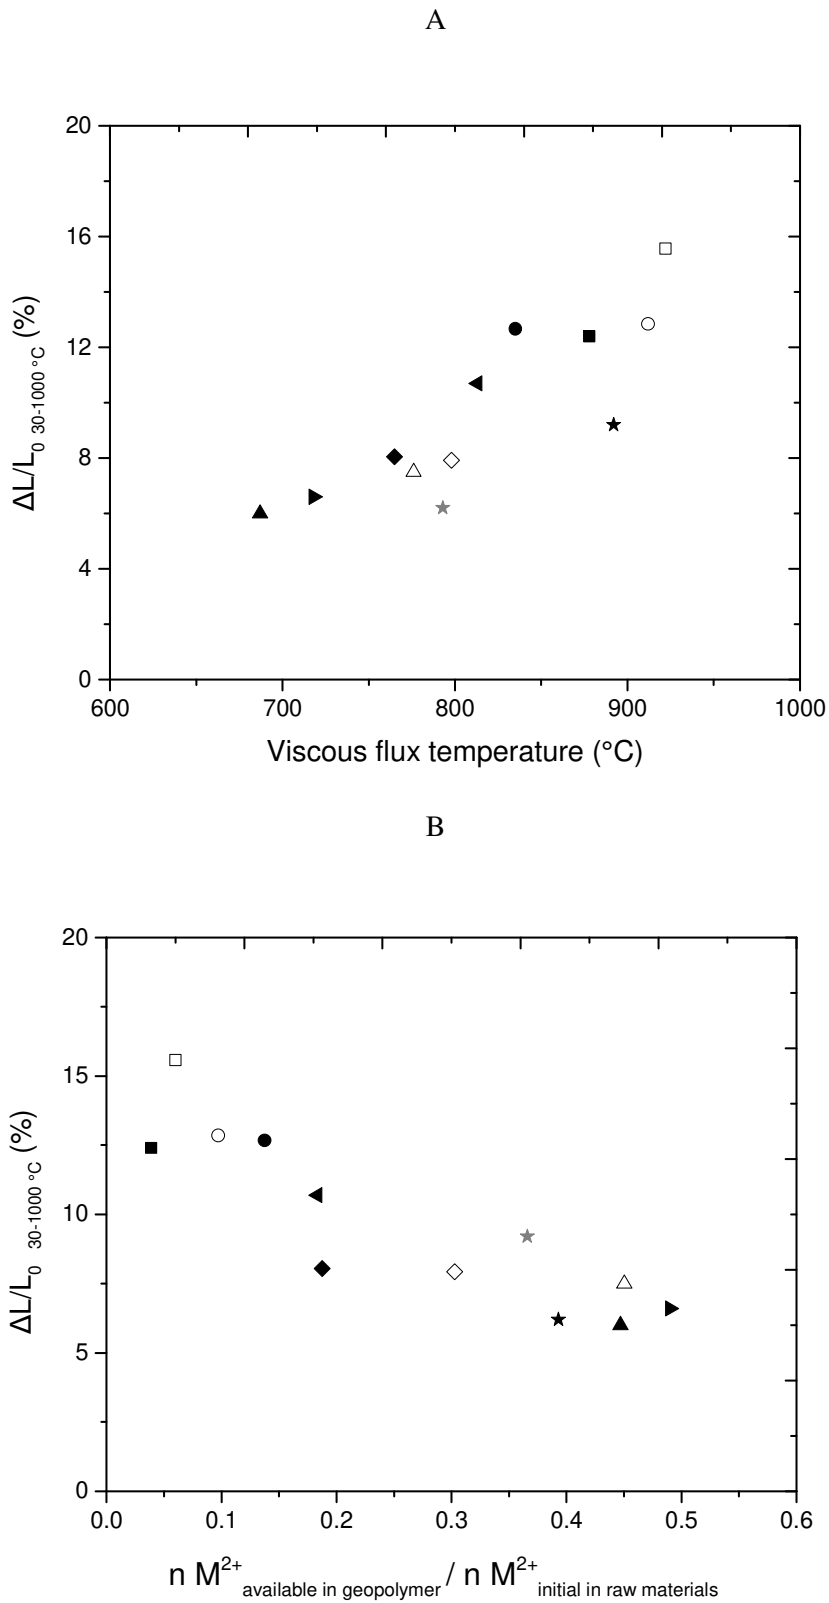


Figure 9: Value of shrinkage between 30 and 1000 °C of geopolymer samples $G(ca_xdo_y)^T$ based on the mixtures calcined at 600 °C (empty) and 750 °C (black) ($ca_{0.1}$ (\circ, \bullet), $ca_{0.5}$ (Δ, \blacktriangle), $do_{0.1}$ (\square, \blacksquare), $do_{0.5}$ (\diamond, \blacklozenge) and $ca_{0.13}do_{0.05}$ (\blacktriangleleft) and extra formulations (\blacktriangleright) from [26] and (\star, \star) from [57] in function of (A) viscous flux temperature and (B) the molar ratio (nM^{2+} available in geopolymers/ nM^{2+} initial in raw materials)

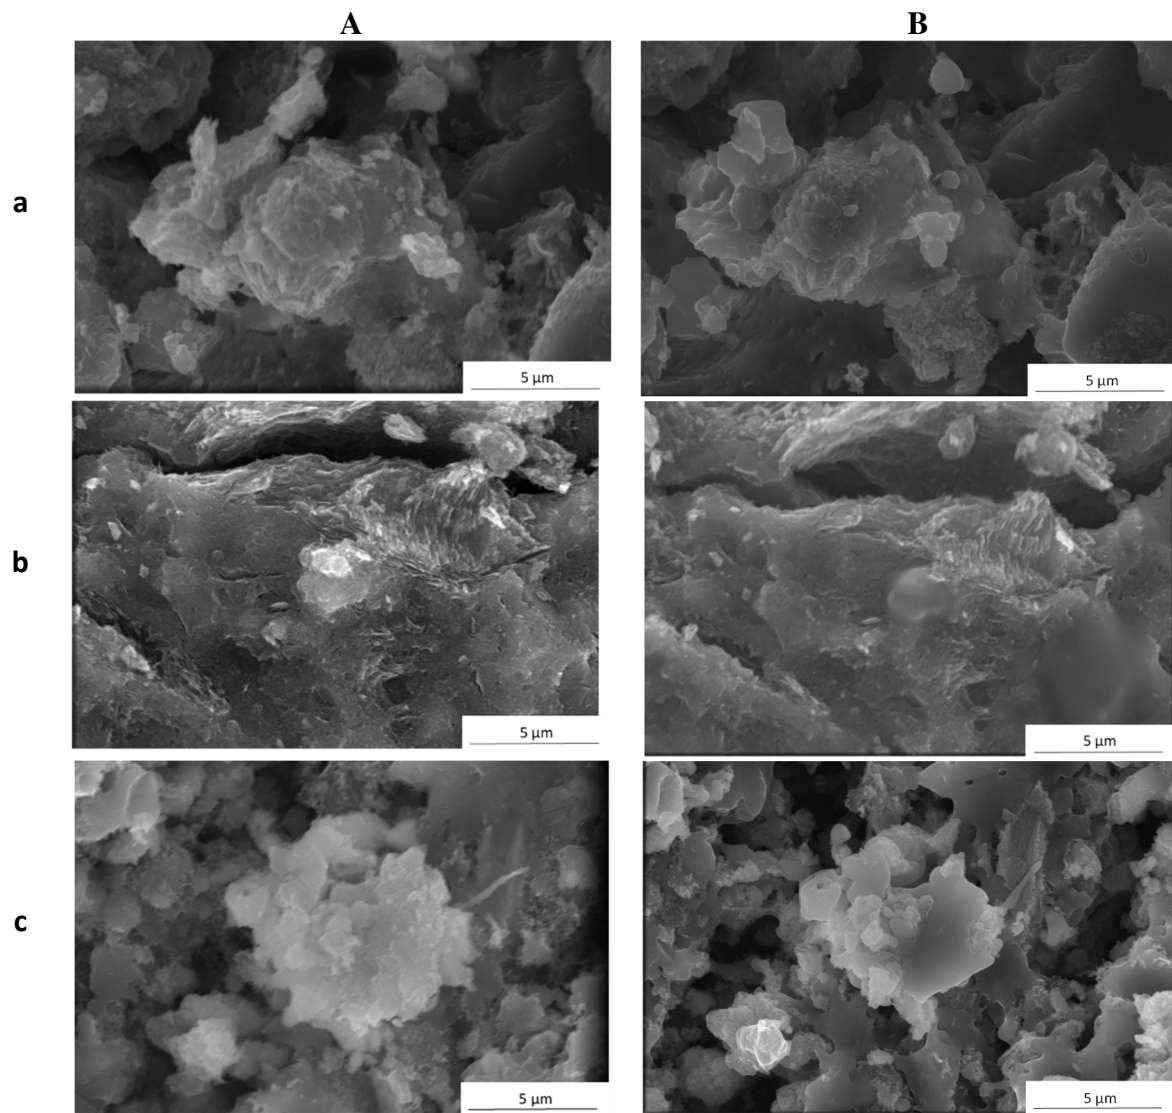


Figure 10: SEM images of geopolymer samples at (A) the temperature of viscous flux appearance and (B) at 1000 °C for (a) $Gd_{0.1}^{750}$, (b) $Gca_{0.13}do_{0.05}^{750}$ and (c) $Gca_{0.5}^{750}$

Table 1. Chemical and physical characteristics of uses raw materials


Raw materials	Supplier	D₅₀ (μm)	S_{BET} (m²/g)	Water demand (μL/g)
Kaolin	Argeco (France)	20	24	530
Calcite	Ceradel (France)	2	2	310
Dolomite		14	1	273

Table 2: Values of decomposition temperature and loss of masse according to DTA-TGA for the different mixtures $ca_xdo_y^T$ based on calcite or / and dolomite

$(ca_xdo_y)^T$	Temperature of treatment (°C)	Mass loss (%)		
		30-200 (°C)	400-600 (°C)	600-800(°C)
ca0.1	25	1.2	3.9	4.2
	600	0.6	0.2	4.9
	750	0.5	0.2	1.6
ca0.5	25	0.6	3.6	22.1
	600	0.4	0.2	22.0
	750	0.3	0.2	22.3
do0.1	25	1.2	6.0	4.3
	600	0.6	0.4	5.4
	750	0.5	0.3	1.7
do0.5	25	0.6	3.7	23.1
	600	0.5	0.3	24.1
	750	0.4	0.2	23.9
ca0.13do0.05	25	1.2	5.1	11.3
	750	0.6	0.3	6.9

Table 3: S_{BET} and D_{50} values of different mixtures ca_xdo_y^T based on calcite or/ and dolomite calcined at 600 and 750 °C

Sample	S_{BET} (m^2/g)	D_{50} (μm)
$\text{ca}_{0.1}^{600}$	18	23
$\text{ca}_{0.5}^{600}$	10	3
$\text{do}_{0.1}^{600}$	20	18
$\text{do}_{0.5}^{600}$	10	5
$\text{ca}_{0.1}^{750}$	19	18
$\text{ca}_{0.5}^{750}$	10	5
$\text{do}_{0.1}^{750}$	19	22
$\text{do}_{0.5}^{750}$	17	18
$\text{ca}_{0.13}\text{do}_{0.05}^{750}$	19	17

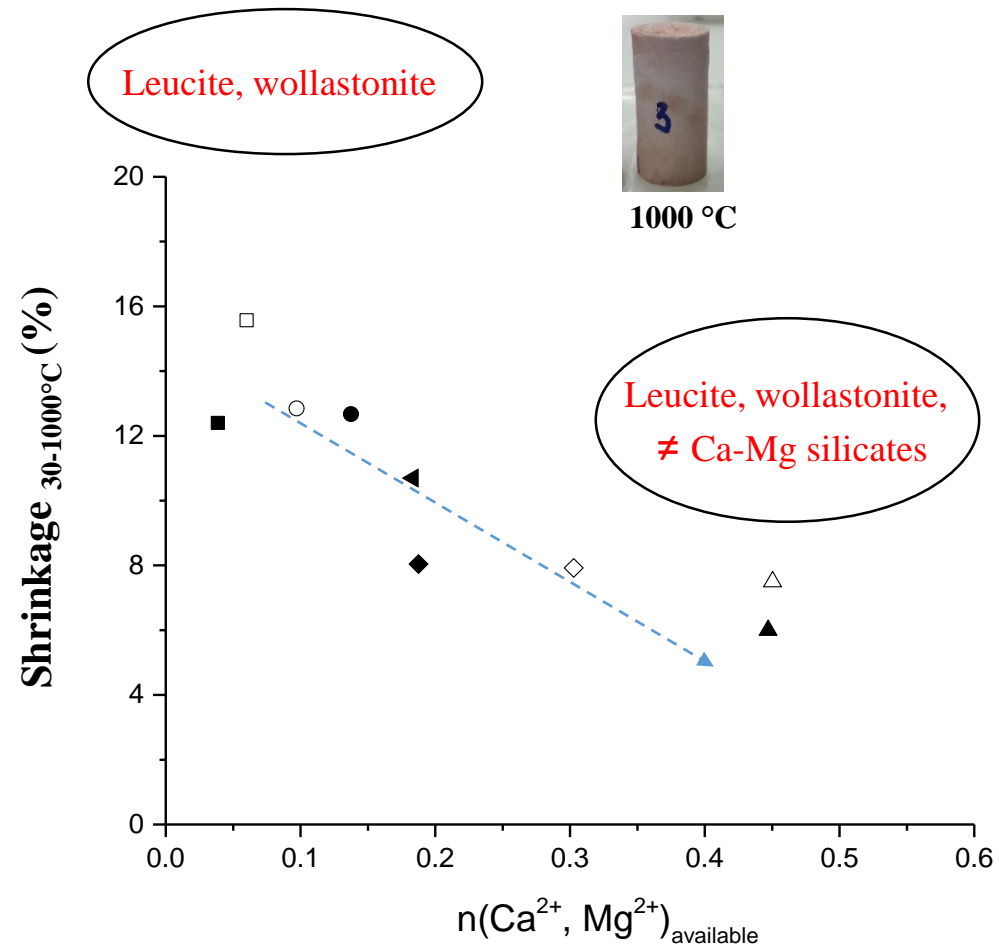

Kaolin-calcite and/or dolomite based geopolymers